



## Dual phase composites for tubular oxygen transport membranes

Martinez Aguilera, Lev; Bjørnetun Haugen, Astri; Kiebach, Wolff-Ragnar

*Published in:*  
Book of Abstracts, Sustain 2017

*Publication date:*  
2017

*Document Version*  
Publisher's PDF, also known as Version of record

[Link back to DTU Orbit](#)

*Citation (APA):*  
Martinez Aguilera, L., Bjørnetun Haugen, A., & Kiebach, W-R. (2017). Dual phase composites for tubular oxygen transport membranes. In *Book of Abstracts, Sustain 2017* [M-18] Technical University of Denmark.

---

### General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.


## Dual phase composites for tubular oxygen transport membranes

Lev Martinez, Astri Bjørnetun Haugen, Wolff-Ragnar Kiebach\*

DTU Energy. Technical University of Denmark. DK-4000 Roskilde, Denmark.

woki@dtu.dk

Dual-phase composites based on ionic-conductors (e.g. ceria and zirconia based materials) and electronic conductors (e.g. perovskites) have demonstrated to be suitable materials for oxygen transport membranes (OTM). Chromite perovskites are promising candidates to be used in OTMs, due to their high electronic conductivity, thermo-chemical stability at high temperatures ( $\sim 1000$  °C) and in reducing environments ( $pO_2 \sim 10^{-20}$  atm). However, their chemical compatibility with ion-conductors in OTMs configuration needs to be further investigated.

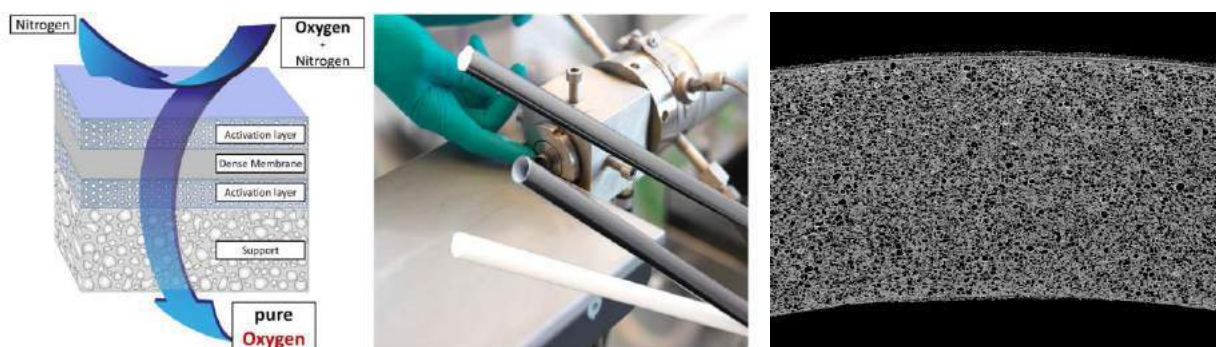

a) Schematic illustration of an oxygen transport membrane. b) Tubular oxygen transport membranes developed at DTU Energy. c) SEM cross section of a tubular oxygen transport membrane.

Composites consisting of 30 vol.% perovskites  $LaCr_{0.85}Cu_{0.10}Ni_{0.05}O_{3-\delta}$  (LCCN) and  $Y_{0.8}Ca_{0.2}Cr_{0.8}Co_{0.2}O_3$  (YCCC), and 70 vol.% ionic conductors  $Zr_{0.802}Sc_{0.180}Y_{0.018}O_{2-\delta}$  (10Sc1YSZ) and  $Ce_{0.9}Gd_{0.1}O_{1.95}$  (CGO10) were chosen as materials. Composites were sintered in air at 1300 °C and stability tests in humidified forming gas at 900 °C for 24 hours were carried out. SEM-EDS and XRD analyses were performed and possible explanations of the degradation mechanism were put forward.

In 10Sc1YSZ-containing composites, low densification, decomposition of the perovskites due to mobility and evaporation of transition metals in the B-side, Ca mobility in YCCC, as well as formation of a La/Zr insulating phase in LCCN were found. In contrast, CGO10-based samples showed > 90% of relative density and higher stability towards reducing conditions. Oxygen permeation tests were performed in both, CGO10-YCCC and CGO10-LCCN composites. Oxygen fluxes up to  $0.4 \text{ Nml}\cdot\text{cm}^{-2}\cdot\text{min}^{-1}$  ( $0.3 \mu\text{mol}\cdot\text{cm}^{-2}\cdot\text{s}^{-1}$ ) were obtained at 950°C in air/ $N_2$  gradient when using 1 mm thick pellets. These results indicate that CGO10-based dual-phase composites are promising OTM materials which require further research for improvement.

Literature: [1] Julbe, A. et. al. Catalysis Today, 104 (2005), 102-113. [2] Den Exter, M. J., et al. Inorganic Membranes for Energy and Environmental Applications, 2009, 27–51. [3] Gupta, S. et al. Materials Science and Engineerig, 90 (2015), 1–36. [4] Suvorov, S.A. et al. Refractories and Industrial Ceramics, 45-2 (2004), 94-99. [5] Kawada, et al. Solid State Ionics, 50 (1992), 189-196.